

Preparation and characterization of Polyhydroxyalkanoates (PHA) and Polylactide (PLA) blends

Thibaut Gérard, Tatiana Budtova

► **To cite this version:**

Thibaut Gérard, Tatiana Budtova. Preparation and characterization of Polyhydroxyalkanoates (PHA) and Polylactide (PLA) blends. 27th World Congress of the Polymer Processing Society, May 2011, Marrakech, Morocco. 4 p. hal-00678829

HAL Id: hal-00678829

<https://hal-mines-paristech.archives-ouvertes.fr/hal-00678829>

Submitted on 14 Mar 2012

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Preparation and characterization of Polyhydroxyalkanoates (PHA) and Polylactide (PLA) blends

T. Gérard^{a,*}, T. Budtova^a

^a Mines ParisTech, Centre de Mise en Forme des Matériaux (CEMEF), CNRS UMR 7635, BP 207, 1 rue Claude Daunesse, 06904 Sophia Antipolis Cedex

*Corresponding author: thibaut.gerard@mines-paristech.fr

Abstract. Polylactide (PLA) and poly(hydroxybutyrate-co-hydroxyvalerate) (PHBV) blends were prepared in different compositions by melt mixing. The miscibility of the two components was first characterized by differential scanning calorimetry (DSC) experiments, which showed the immiscibility of the components for all blend compositions. The morphology was studied using scanning electron microscope (SEM) and optical microscopy in reflection. Nodular and co-continuous morphologies were observed depending on the composition. The rheology of the pure polymers and of the PLA/PHBV blends was investigated in the dynamic mode. The results showed a significant role of the interfaces with an increase of the complex viscosity at small frequencies.

Introduction

Nowadays, petrochemical based polymers are associated with a lot of environmental concerns and sustainability issues. An important part of those polymers are used for short-lived applications by the packaging industry. When these materials are incinerated, they participate to the release of CO₂ in the atmosphere, which increase the greenhouse effect and the global warming. Moreover, a non negligible part of the plastics accumulate in the oceans and impact the ecosystems.

Biotechnological polymers such as polylactides (PLA) or polyhydroxyalkanoates (PHA) are alternatives to petroleum-based polymers and represent an attractive growing market. These sustainable polymers are becoming more competitive due to the increase of the price of the oil barrel. The capacity for the production of biobased plastics, which was estimated at 300 000 tones in 2008, is expected to reach more than 3 million tones in 2020 [1].

Polyhydroxyalkanoates are polyesters directly produced by numerous microorganisms by bacterial fermentation of sugars or lipids. These microorganisms accumulate PHA as water insoluble inclusions in their body as a carbon and energy storage material [2].

Polylactide is synthesized from lactic acid, which is obtained from renewable resources such as corn, starch or maize. Polylactide is now produced on a large scale and used for various applications in different domains: packaging, medicine, agriculture, textiles...

The blending of polymers is a useful way of obtaining new materials with improved properties, less costly than chemical modifications or synthesis of tailor-made copolymers. The physical and mechanical properties of blends can be easily modified by choosing the polymers and varying the composition of the blend.

Most of the studies on PLA and PHA blends that have been reported in the literature concern the blends prepared by solvent casting. Only few studies have been conducted on the preparation and characterization of PLA/PHA blends by melt mixing [3] despite the fact that both polymers are thermoplastics and their processing is similar to the classical oil-based polymers.

In the present research work, blends of a poly(hydroxybutyrate-co-hydroxyvalerate) (PHBV) and a polylactide have been studied. These blends have been prepared by melt-mixing of the initial polymers in various proportions. The aim of this study is to understand the thermal, morphological and rheological properties of PLA/PHBV blends.

EXPERIMENTAL

Materials

PHBV was purchased from Tianan Biological Materials Co. Polylactide (3051D, injection molding grade) used in the study was supplied by NatureWorks Co. Ltd., USA.

Blend preparation

The PLA/PHBV blends were prepared by melt mixing in an internal batch mixer (Haake Rheomix 600). The PLA/PHBV compositions tested were 0/100, 10/90, 20/80, 30/70, 40/60, 50/50, 60/40, 70/30, 80/20, 90/10 and 100/0 (w/w).

Methods

Thermal analysis was performed on a Perkin Elmer DSC 8500 differential scanning calorimeter in order to assess the thermal properties of the blends (T_g , T_f) and to study the miscibility of the two components system. The samples were first heated from -40°C up to 200°C at a heating rate of $10^\circ\text{C}/\text{min}$ under nitrogen atmosphere and maintained at this temperature for 2 min to eliminate thermal history. The samples were then cooled to -40°C at a cooling rate of $10^\circ\text{C}/\text{min}$ and heated again to 200°C at $10^\circ\text{C}/\text{min}$.

The morphologies of the blends were investigated using a PHILIPS XL-30 ESEM scanning electron microscope. The samples were fractured in liquid nitrogen and sputter-coated with gold. Optical microscopy in reflection on polished samples was also used to observe the different blends structures. Rheological measurements were carried out on ARES rheometer (TA Instruments) using 25 mm diameter parallel plates. Before testing, the polymer blended samples were cut into pieces and compression molded by a hot plates hydraulic press to obtain 2 mm thick and 25 mm diameter discs. All rheological measurements were performed under the temperature of 175°C . Dynamic strain sweep tests were performed in a first step to determine the linear viscoelastic domain. Then, dynamic frequency sweep tests were carried out from 100 to 0.1 or 0.01 rad/s. Dynamic time sweep tests were also done during 2 hours to assess the thermal stability of the two blending partners.

RESULTS AND DISCUSSION

Miscibility of PLA/PHBV blends

Differential scanning calorimetry was used to study the miscibility of the PLA/PHBV blends.

The melting temperature (T_m) of the two blending partners remained constant and independent of the blend composition. Two main melting endotherms were found at around 150 and 170°C , corresponding to the melting temperatures of PLA and PHBV.

The glass transition temperature (T_g) of PLA was around 60°C and did not show any variation with the blend composition. The determination of the glass transition temperature of the PHBV was difficult with the chosen heating rate; however, T_g of PHBV could be evaluated to 4°C .

The glass transition and melting temperature of PLA and PHBV were almost constant for all the range of compositions tested, showing that the PLA/PHBV binary blends are immiscible in the melt.

Thermal degradation of PHBV

It is known that polyhydroxyalkanoates have a very narrow processing window because of their thermal degradation, which limits their commercial use. Thermal degradation occurs rapidly at a given processing temperature, which is very close to the melting temperature. For instance, the acceptable residence time for poly(3-hydroxybutyrate) in the processing equipment is only a few minutes [4].

The rheological data obtained in our study showed clearly that thermal stability of PHBV is extremely low. **Fig. 1** displays the evolution of the complex viscosity of PLA and PHBV as a function of oscillatory shear time at 175°C . The decrease of the viscosity of PHBV is dramatic: η^* dropped by more than one decade in one hour.

The thermal degradation was confirmed by the assessment of the molecular weights of PHBV samples using a gel permeation chromatography (GPC) kindly performed by Arkema. The PHBV samples were collected after dynamic tests lasting different times. M_w was divided by two after a 10 min test and by four after one hour of rheological experiment. This decrease of molecular weight with test time can be attributed to the decrease of the polymer length via chain scission.

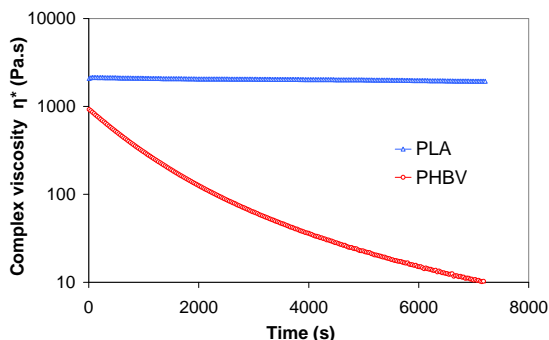


Fig. 1. Complex viscosities of PLA and PHBV as a function of oscillatory shear time ($T=175^{\circ}\text{C}$, $\omega=1$ rad/s, $\varepsilon=5\%$).

Morphology observation

The blend morphologies were first investigated using a scanning electron microscope (SEM). **Fig. 2** presents a SEM micrograph of a fractured surface for a 70/30 PLA/PHBV blend. We clearly distinguished spherical droplets of PHBV in the PLA matrix. Besides, the adhesion between the two phases was bad. Blends with minor phase below 30 wt% showed a nodular structure. On the contrary, 60/40, 50/50 and 40/60 blends seemed to exhibit a co-continuous structure.

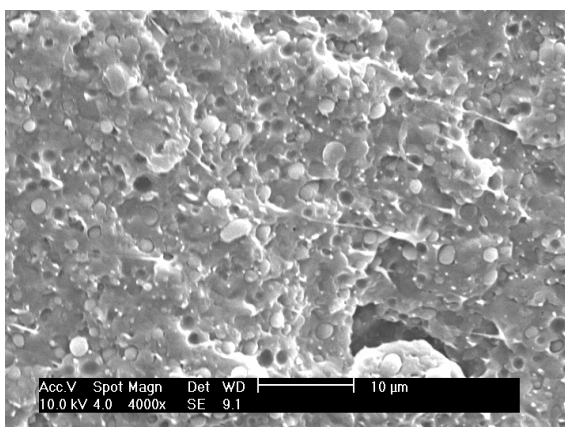


Fig. 2. SEM micrograph of a PLA/PHBV fractured sample with weight ratio 70/30.

Due to the similar structure of the two polyesters, the contrast between the two phases was limited. Moreover, selective dissolution did not work. To observe the morphology of the PLA/PHBV blends more clearly, samples were finely polished and observed with a microscope in reflection. **Fig. 3**

shows an image of a 50/50 blend sample. This blend showed a co-continuous structure, with two interpenetrated phases. The same morphology was observed for the 40/60 and 60/40 compositions.

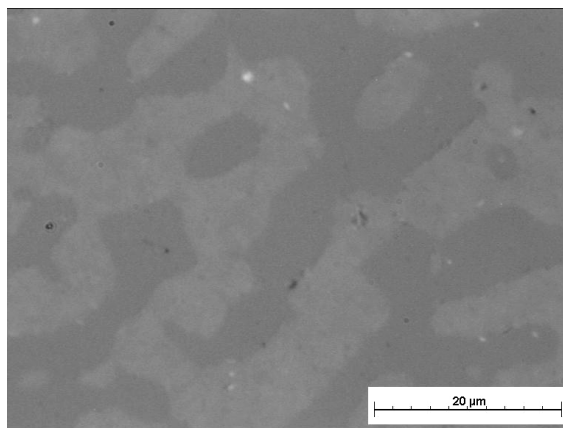


Fig. 3. Reflection optical microscopy image of a PLA/PHBV polished sample with weight ratio 50/50.

Rheological behavior of the blends

Dynamic frequency sweep tests were carried out to characterize the viscoelastic properties of the PLA/PHBV blends at 175°C . **Fig. 4** displays the elastic modulus (G') and the complex viscosity (η^*) curves for the pure polymers and their blends in different compositions (20/80, 50/50 and 80/20).

Firstly, both G' and η^* were the highest for pure PLA and increased with the PLA content in the PLA/PHBV blend. The elastic modulus of the pure PLA (100/0) and the pure PHBV (0/100) showed a typical terminal behavior with a slope of around 2 at low frequencies (Fig. 4a). For the blends containing a small quantity of PLA or PHBV, we clearly observed a shoulder for G' . It should correspond to the relaxation of droplets of the dispersed phase in the matrix. We noticed the formation of a G' plateau at low frequencies for the blends containing nearly as much PLA as PHBV. Interfaces between PLA and PHBV play thus a very significant role in the rheological behavior of the blend. This is supported by the significant increase of the complex viscosity at low frequencies for the 50/50 blend (Fig. 4b).

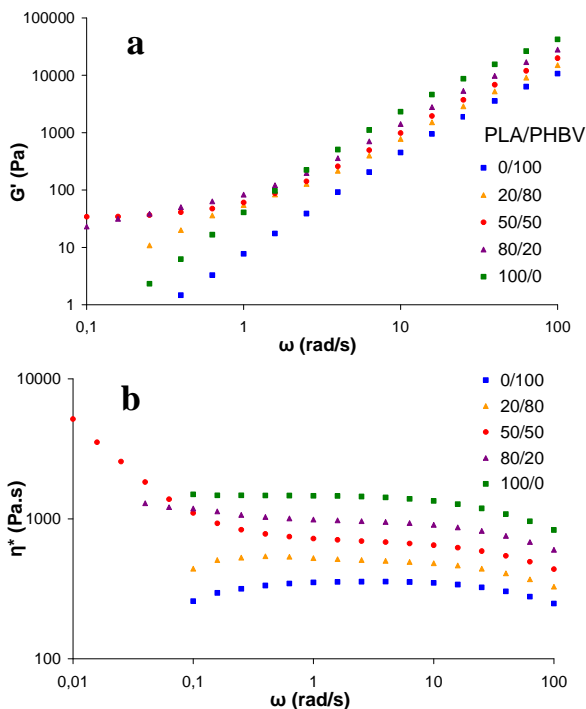


Fig. 4. (a) Dynamic storage modulus (G') and (b) complex viscosity (η^*) of PLA/PHBV blends as a function of oscillatory shear frequency ($T=175^\circ\text{C}$)

Conclusion

In this study, blends of PHBV and PLA have been prepared by melt mixing. Miscibility, phase morphology and rheological behavior were investigated by DSC, SEM and oscillatory rheometry. The DSC experiments showed the immiscibility of the two polymers for all compositions. Two different morphologies have been observed: nodular structure and co-continuous structure. Rheological testing has showed that thermal stability of PHBV was extremely low and that interfaces played a significant role in PLA/PHBV blends. Work on the effect of adding a commercial compatibilizer on the rheological and morphological properties of PLA/PHBV blends is in progress.

Acknowledgments

The present work is performed in the frame of the Industrial Chair on Bioplastics, organised by CEMEF/MINES ParisTech and supported by Arkema, L'Oreal, Nestlé, PSA Peugeot Citroën and Schneider Electric through the "Fondation des

Industries Minérales, Minières et Métallurgiques Françaises".

References

1. L. Shen, J. Haufe, M. K. Patel, *Product overview and market projection of emerging bio-based plastics*, PRO-BIP 2009, Utrecht University (2009).
2. K. Sudesh, H. Abe, Y. Doi, *Prog. Polym. Sci.*, **25**, 1503 (2000)
3. K. M. Schreck, M. A. Hillmyer, *Journal of Biotechnology*, **132**, 287(2007)
4. I. Janigová, I. Lacík, I. Chodák, *Polym. Degrad. Stab.*, **77**, 35 (2002)