



# On modeling of thermal embrittlement in PWR steels using the local approach to fracture

Antoine Andrieu, André Pineau, Pierre Joly, François Roch

## ► To cite this version:

Antoine Andrieu, André Pineau, Pierre Joly, François Roch. On modeling of thermal embrittlement in PWR steels using the local approach to fracture. 13th international conference on fracture, Jun 2013, Beijing, China. 10 p. hal-00853417

**HAL Id: hal-00853417**

**<https://minesparis-psl.hal.science/hal-00853417>**

Submitted on 14 Nov 2013

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

## On Modeling of Thermal Embrittlement in PWR Steels using the Local Approach to Fracture

**Antoine Andrieu<sup>1</sup>, André Pineau<sup>1\*</sup>, Pierre Joly<sup>2</sup>, François Roch<sup>2</sup>**

<sup>1</sup> Centre des Matériaux, Mines ParisTech, UMR CNRS 7633, BP 87, 91003 Evry Cedex, France

<sup>2</sup> AREVA, Tour Areva, 1 Place Jean Millier, 92084 Paris La Défense

\* Corresponding author: andre.pineau@ensmp.fr

**Abstract** Experiments on Charpy and CT specimens were carried out on one heat of A533B steel under two conditions: (i) as received, and (ii) thermally aged (450°C – 5000h). A shift of the ductile to brittle transition temperature (DBTT) was measured after aging. In both cases SEM observations showed that fracture occurred both by intergranular and transgranular cleavage fracture modes when the materials were tested at sufficiently low temperature. Detailed examinations revealed that intergranular fracture was associated with micro-segregated zones, enriched in carbon and phosphorus. A recent model developed by the authors for predicting the fracture toughness of inhomogeneous materials was applied to describe the large scatter related to the bimodal failure modes observed in both conditions and the DBTT shift after aging. It is shown that thermal aging produces a slight decrease of the critical cleavage stress (due to the crossing of grain boundaries embrittled by phosphorus segregation) and a larger decrease of the critical intergranular fracture stress. The McLean-Guttmann- Miltzer model is used to predict the kinetics of segregation during aging. An attempt is made to show how these results can be used to model DBTT variations under in-service conditions.

**Keywords** Ductile to brittle transition, intergranular, phosphorus segregation

### 1. Introduction

It is often noticed the presence of segregated zones (S.Z) in large components used for the fabrication of pressurized water reactors (PWR) (see e.g. [1, 2]. These SZs are linked to the solidification process of large ingots. They are enriched in the alloying elements (Mn, Ni, Mo, C, etc.) present in the steel. They are also enriched in impurities, such as P which may segregate at grain boundaries during aging. These local microstructural modifications can generate a bimodal fracture process (cleavage and intergranular fracture), as shown elsewhere [2].

Brittle (cleavage and intergranular) fracture in homogeneous ferritic (or bainitic) steels has been investigated by many authors, for a review see e.g. [3]. The seminal work by Beremin [4] has shown that in a homogeneous material the fracture toughness,  $K_{IC}$  obeys a size effect given by  $K_{IC}^4 B = \text{constant}$ , where  $B$  is the thickness of the specimen, while the scatter in test results can be described by a Weibull law. The probability of failure can be expressed as:

$$P_r = 1 - \exp \left[ - \frac{K_{IC}^4 B \sigma_o^{m-4} C_{m,n}}{V_o \sigma_u^m} \right] \quad (1)$$

Where  $\sigma_o$  is the yield strength of the material,  $m$  is the Weibull shape factor,  $C_{m,n}$  is a parameter depending both on material work-hardening exponent,  $n$ , and the Weibull shape factor,  $m$  (see [5] for detailed values of  $C_{mn}$ .)  $V_o$  is a representative volume and  $\sigma_u$  is the Weibull scale factor. Recently it has been shown how Eq.1 must be modified in the presence of inhomogeneities leading to local intergranular fracture [2].

The main aim of the present study is the application of these recent modifications of the original

Beremin model to predict the variation of fracture toughness with temperature. One heat of 18 MND5 grade steel (type A533B) was used for this purpose. The material (a 100mm thick hot-rolled plate) was tested in the as-received condition and after aging at 450°C for 5000 hours. This aging heat treatment was introduced to reinforce the segregation of phosphorus at grain boundaries and to decrease the grain boundary fracture resistance. The McLean [6]–Guttmann [7] theories for impurity intergranular segregation was used to calculate the grain boundary enrichment in phosphorus and in carbon under isothermal conditions. These theoretical values were compared to experimental values determined by Auger spectrometry. The interaction between C and P atoms was adjusted from this comparison. Therefore the approach developed in the present study contributes to an improvement in the prediction of the shift in DBTT with thermal aging.

## 2. Material and experimental procedures

The composition of the investigated steel is (in weight %): C = 0.192, Mn = 1.44, Ni = 0.683, Mo = 0.473, Cr = 0.194, Si = 0.249, S = 0.0053, P = 0.010. It was received as a thick plate (100 mm) produced for simulating welding operations. This material was used in the past for the manufacturing of steam generator secondary pressure vessel, and is very close to plates used in the past for pressurizer vessels. The material was given the conventional heat-treatments applied to PWR components, including the final stress-relieving heat-treatment (615°C-Air cooling at ~ 30°C /hour). The prior austenite grain size was between 20 and 30  $\mu\text{m}$ . The yield strength determined at RT was 490 MPa.

The microstructure of the material is shown in Fig.1. Segregated zones (SZ) aligned along the rolling direction (L) and distant of about 0.2 mm in the short-transverse (ST) directions are observed in Fig.1a. This is the consequence of micro-segregations of alloying elements during solidification, deformed by the rolling process. The dark zones are much harder than the matrix (~ 300 HV instead of ~ 210 HV) (Fig.1b). They are enriched in all alloying elements (C, Mn, Mo, Si) and in P as revealed by microprobe analysis (Fig.1b). The surface fraction covered by these segregated zones is about 10%. SEM and Auger spectrometry were used to examine the fracture surfaces and to determine the amount of phosphorus segregated along the grain boundaries.

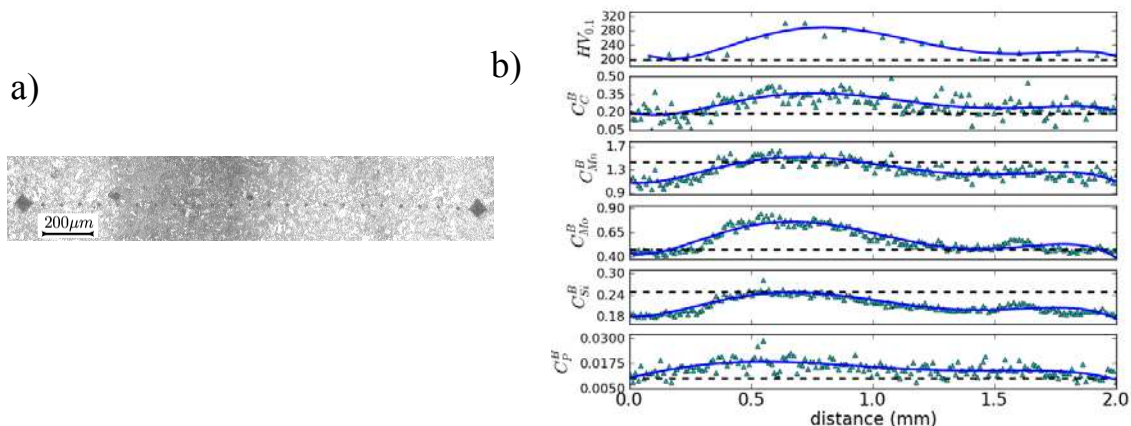


Figure 1. a) Optical micrograph showing two segregated zones aligned along the rolling direction; b) Microprobe analysis across one segregated zone showing the bulk concentration  $C^B$  in carbon, manganese, molybdenum, silicon and phosphorus. The variations of micro-hardness (100g) are also shown.

### 3. Results – Mechanical tests and fractography

The results obtained on Charpy specimens and on CT specimens, tested along the T (transverse) – L orientation are reported in Fig. 2. A shift of the ductile to brittle transition temperature (DBTT) measured at 41J appears in Fig. 2a when comparing the as-received and the aged conditions. This shift is of about 39°C. Similarly the fracture toughness determined on CT<sub>20</sub> specimens is lowered by aging (Fig. 2b and c). In these figures we have also reported the probabilities to fracture for 5%, 63% and 95% determined from the master curve (MC) analysis [8, 9]. The temperature  $T_o$  at which  $K_{JC} = 100 \text{ MPa m}^{1/2}$  is shifted from  $-124^\circ\text{C}$  in the as-received condition to  $-91^\circ\text{C}$  in the aged condition. The scatter in the aged material is much wider than in the as-received material. In particular it is noticed that the MC analysis is unable to describe this large scatter.

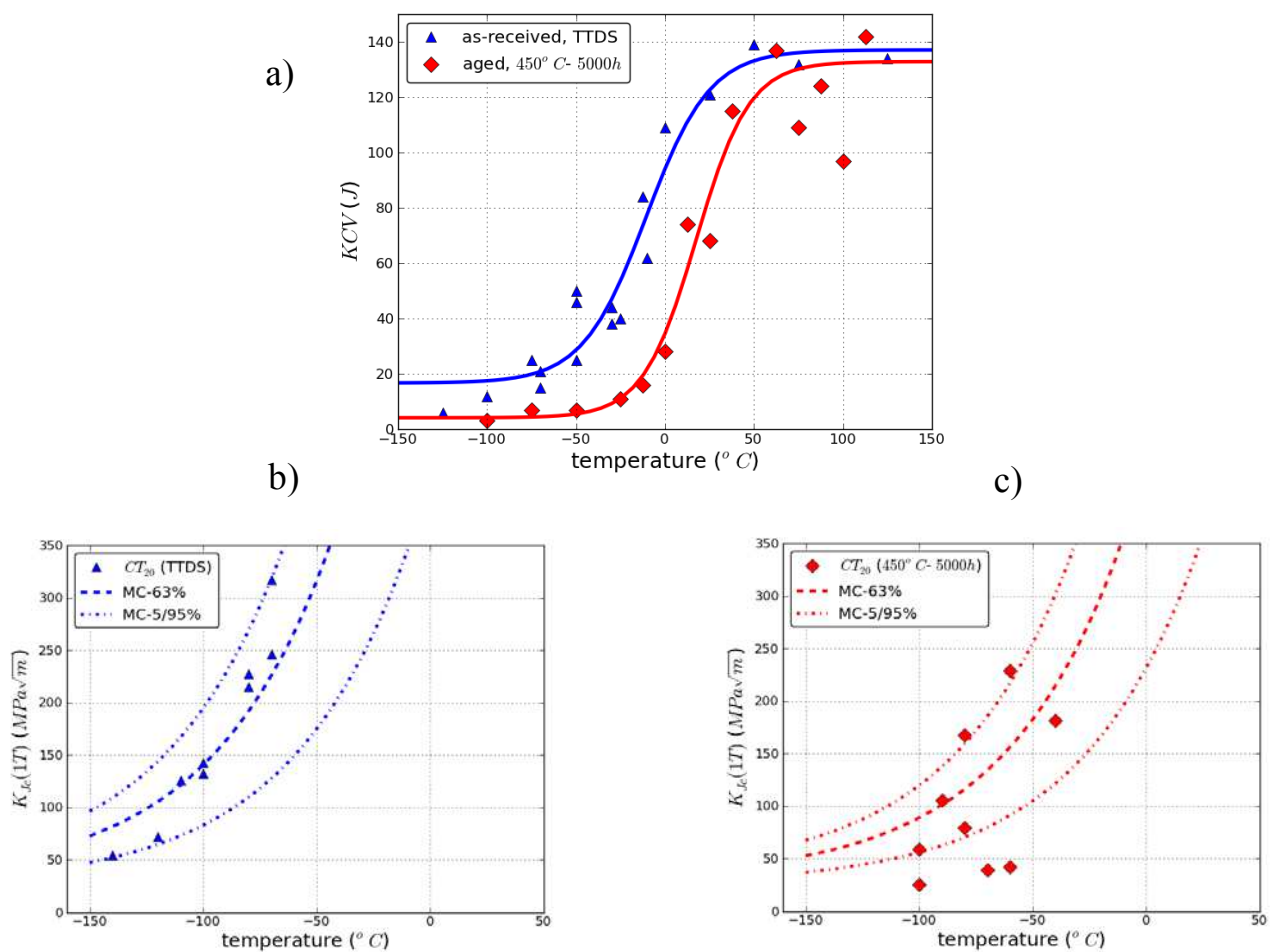


Figure 2. a) Charpy tests in as-received and aged (450°C – 5000 h) conditions; b) Fracture toughness,  $K_{JC}$  (thickness) determined on CT 20 mm thick specimens as a function of temperature in the as-received material; c) Fracture toughness  $K_{JC}$  on CT20 mm thick specimens in the aged (450°C – 5000 h) condition. The probabilities  $P_r = 5\%, 63\%, 95\%$  determined from the Master Curve (MC) are also drawn.

Fracture surface examination of Charpy and CT specimens tested at relatively low temperature showed the presence of elongated zones aligned along the L direction (Fig. 3a) in which the fracture

mode was intergranular (Fig. 3c). This local intergranular fracture mode was observed in both conditions. These zones correspond to the SZ evidenced in Fig. 1a. They contained very often MnS inclusions (Fig. 3b) and were surrounded by cleavage facets as observed in Fig. 3b. This observation is thus similar to previous examinations on a segregated PWR material (see Fig. 1 in [2]). The ratio of intergranular/transgranular cleavage fracture was similar in both conditions.

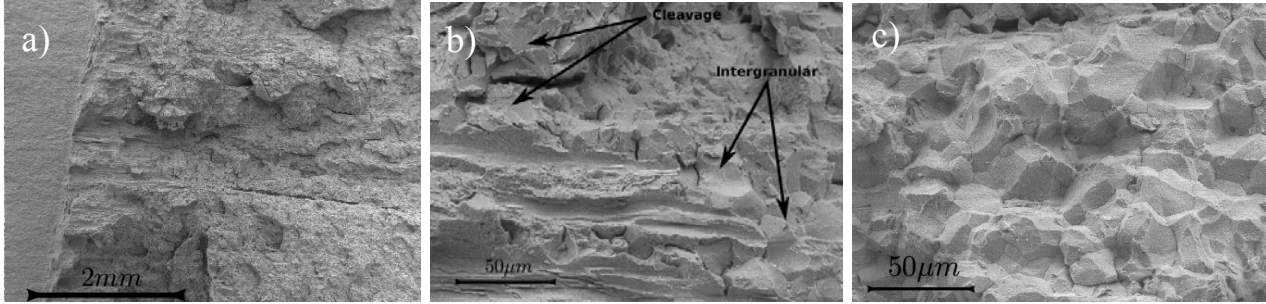


Figure 3. SEM observations: a) and b) As received material; c) Aged (450°C – 5000 h) condition.

#### 4. Intergranular segregation – Results and theoretical considerations

Auger spectrometry measurements showed that the phosphorus concentration (atomic %) at grain boundaries increased significantly between the as-received condition ( $C_p^{gb} = 12.5 \pm 6\%$ ) and the aged condition ( $C_p^{gb} = 23 \pm 9\%$ ). The grain boundary concentration in carbon tended to decrease with aging ( $C_c^{gb} = 37 \pm 14\%$  in the as-received condition compared to  $C_c^{gb} = 28 \pm 10\%$  in the aged condition).

Full details about these measurements can be found elsewhere [10]. Intergranular P phosphorus segregation was shown to occur during cooling after the stress-relieving heat treatment. The relatively low cooling rate ( $\sim 30^\circ\text{C/h}$  below  $615^\circ\text{C}$ ) thus produces temper-embrittlement effect in the segregated zones enriched in phosphorus.

The theory of isothermal intergranular segregation has been developed by McLean [6] in his pioneering work. This theory was extended by Guttman [7] to account for the interaction of an impurity element (here P) with other elements, in particular carbon atoms. A comprehensive review of these theories can be found in the recent book of Lejcek [11]. The grain boundary concentration at equilibrium,  $C_i^{gb,eq}$  in a system containing N elements in solid solution  $C^B$  can be written as:

$$\frac{C_i^{gb,eq}}{1 - \sum_{j=0}^N C_j^{gb,eq}} = \frac{C_i^B}{1 - \sum_{j=0}^N C_j^B} \exp\left[-\frac{\Delta G_i^{seg}}{RT}\right] \quad (1)$$

The segregation energy  $\Delta G_i^{seg}$  is expressed as:

$$\Delta G_i^{seg} = \Delta G_i^o + \Delta G_i^E = \Delta H_i^o - T\Delta S_i^o + \Delta G_i^E \quad (2)$$

where  $\Delta G_i^E$  represents the deviation from an ideal system due to the presence of elements other than the impurity, i.

In a binary system, such as Fe-C or Fe-P, the kinetics of segregation  $C^{gb}(t)$  is given by [6]:

$$C^{gb}(t) = C^{gb,eq}(T_2) - C_o(\alpha_2 - \alpha_1) \exp\left[\frac{4Dt}{\alpha_2^2 \delta^2}\right] \operatorname{erfc}\left[\frac{2\sqrt{Dt}}{\alpha_2 \delta}\right] \quad (3)$$

where  $C^{gb,eq}$  is the concentration at equilibrium of the impurity, at temperature  $T_2$ , given by Eq. 1,  $C_o = C^B(t=0)$  is the impurity concentration in the matrix which is assumed to be constant,  $\alpha_1 = C^{gb,eq}(T_1) / C_o$  with  $T_1$  the temperature from which the material is cooled down,  $\alpha_2 = C^{gb,eq}(T_2) / C_o$ ,  $D$  the coefficient of diffusion of the impurity at  $T_2$ ,  $t$  the time and  $\delta$ , the thickness of the grain boundary.

In a ternary system, Guttman [7] assumed that  $\Delta G_i^{seg}$  can be expressed as:

$$\Delta G_i^{seg} = \Delta G_i^o - 2\alpha_{ii} C_i^{gb} + \alpha_{ij} C_j^{gb} \quad (4)$$

where the coefficients  $\alpha_{ii}$  and  $\alpha_{ij}$  describe the interaction between the elements segregating at grain boundaries ( $\alpha_{ii} > 0$  or  $\alpha_{ij} < 0$  correspond to a repulsive interaction which is the situation met with C and P).

The solution for the kinetics of segregation for non-isothermal conditions can be derived from Militzer's work [12].

All terms in Eqs. 1-4 have been determined in the literature:

$$d = 810^{-10} \text{ m}$$

$$D_p = 0.25 \exp\left(-\frac{200000}{RT}\right) \text{ (cm}^2\text{s}^{-1}) \quad [13, 14] \quad (5)$$

$$D_c = 0.003 \exp\left(\frac{76000}{RT}\right) \text{ (cm}^2\text{s}^{-1}) \quad [15] \quad (6)$$

$$\Delta G_p^o = 64273 - 23.7T \text{ (J mol}^{-1}) \quad [13] \quad (7)$$

$$\Delta G_c^o = 16752 + 40.9T \text{ (J mol}^{-1}) \quad [13] \quad (8)$$

$$\alpha_{cc} = 4000 \text{ J mole}^{-1}; \quad \alpha_{pp} = 1500 \text{ J mole}^{-1}; \quad \alpha_{cp} = -4500 \text{ J mole}^{-1} \quad [10, 16] \quad (9)$$

The McLean-Guttman-Militzer model has been applied to our steel with  $T_f = 888 \text{ K}$ ,  $C_c^B = 80 \text{ ppm}$  (Wt %) and  $C_p^B = 150 \text{ ppm}$  (Wt %) for predicting the C and P grain boundary concentration in the

as-received condition ( $t = 0$ ) and during aging at 450°C. Full details can be found elsewhere [10]. The results are compared to experimental measurements in Fig. 4 where it is observed that in the as-received condition ( $t = 0$ ), phosphorus and carbon atoms are already segregated. Carbon atoms desegregate during aging while phosphorus concentration is increasing. This results from the repulsive interaction between C and P atoms (Eq. 9). The calculated values are in good agreement with the experimental values.

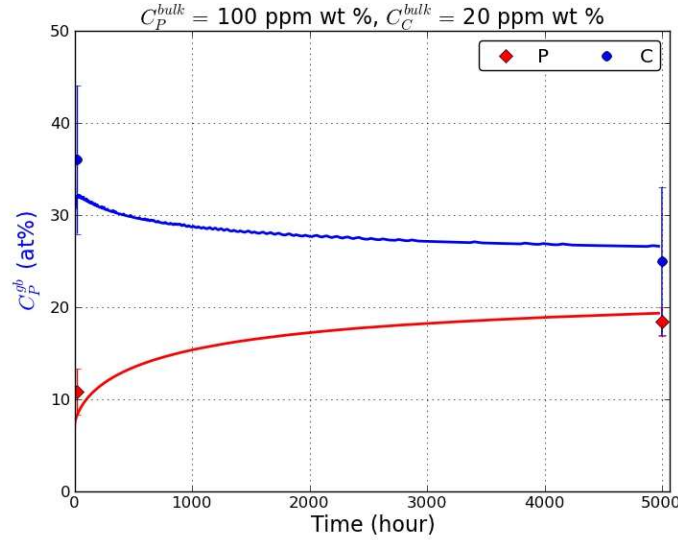


Figure 4. Phosphorus (P) and carbon (C) concentration at grain boundaries (expressed in atomic %) a function of aging time at 450°C. Experimental results and calculated curves.

## 5. Prediction of fracture toughness – Influence of impurity segregation

It has been shown that the fracture mode of our material in the DBTT regime was bimodal: transgranular cleavage and intergranular. A recent model has been proposed for this situation [2]. However this model includes a number of parameters (Weibull shape factors, critical cleavage and intergranular fracture stress,  $\sigma_u$ ) which have to be discussed first. This is related to the fact that aging produces a variation in the concentration of impurities (C and P) segregated along the grain boundaries. It is well to remember that C atoms produce a strengthening effect of the grain boundaries while P atoms have an opposite effect [17].

It has been shown previously that the intergranular fracture stress decreases linearly with  $C_p^{gb}$  [18, 19] as soon as the grain boundary concentration in P is larger than about 10 at %. These results can be used to predict the variation of the fracture toughness with aging using the kinetics models developed in the preceding section.

The cleavage fracture stress is also dependent on the grain boundary composition as explained below. This effect is related to the crossing of grain boundaries by cleavage cracks, which has already been studied in some detail by Qiao [20, 21]. This crossing depends on the misorientation between two adjacent grains, as depicted in Fig. 5 where the tilt,  $\phi$ , and the twist,  $\psi$ , components



between two grains are defined. The tilt component produces only a deviation of the crack front. The twist component produces a segmentation of the crack front and the formation of ridges, as observed in Fig. 6a and as schematically depicted in Fig. 6b. Complete crossing of the grain boundary by the cleavage crack in grain 1 necessitates in these conditions that the intergranular “triangles” are also broken. The = global? cleavage stress is thus also dependent on the local composition of the grain boundaries.

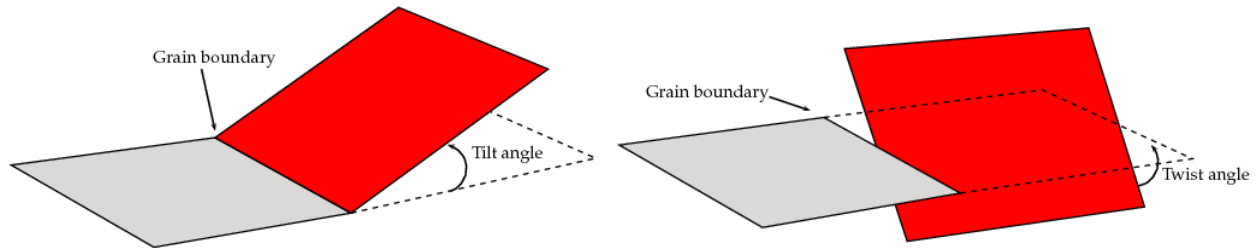


Figure 5. Notations for tilt and twist grain boundaries.

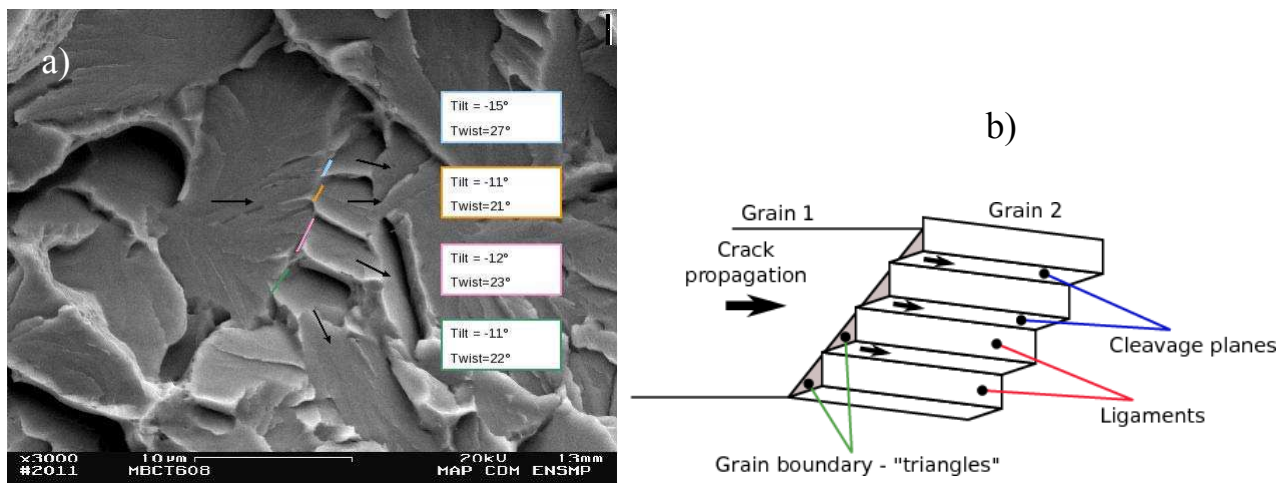


Figure 6. a) SEM observations showing the formation of bifurcations when a cleavage crack crosses a grain boundary. Four ridges are formed. The values of the tilt and twist angles determined by quantitative stereoscopy are given; b) Sketch.

A model was developed to analyze this phenomenon of crossing of twisted grain boundary cleavage cracks. It is out of the scope of the present paper to describe in detail this model which is schematically shown in Fig. 7. The grain boundary crossing process includes four steps. The cleavage crack in grain 1 is approaching the grain boundary in step 1. Cleavage microcracks are assumed to nucleate on (001) planes in grain 2 (step 2). These microcracks propagate in the second grain and break the “triangles” remaining along the grain boundary and which belong to the grain boundary itself (step 3). This generates a perturbed crack front which is still attached to the grain boundary by remaining ligaments. In step 4 the perturbed crack front propagates and leads to final fracture. The model is based on an energy balance between the driving energy corresponding to the strain energy release rate of the perturbed crack and the dissipated energy. This energy includes



three contributions: (i) the cleavage surface energy on the facets of the second grain, (ii) the intergranular energy of the “triangles”, and (iii) the energy spent in breaking the remaining ligaments. This model predicts that the number of segmentations along a given grain boundary is an increasing function of  $\psi$ , as observed experimentally [10] and that the = global? cleavage stress is also increasing with  $\psi$ .

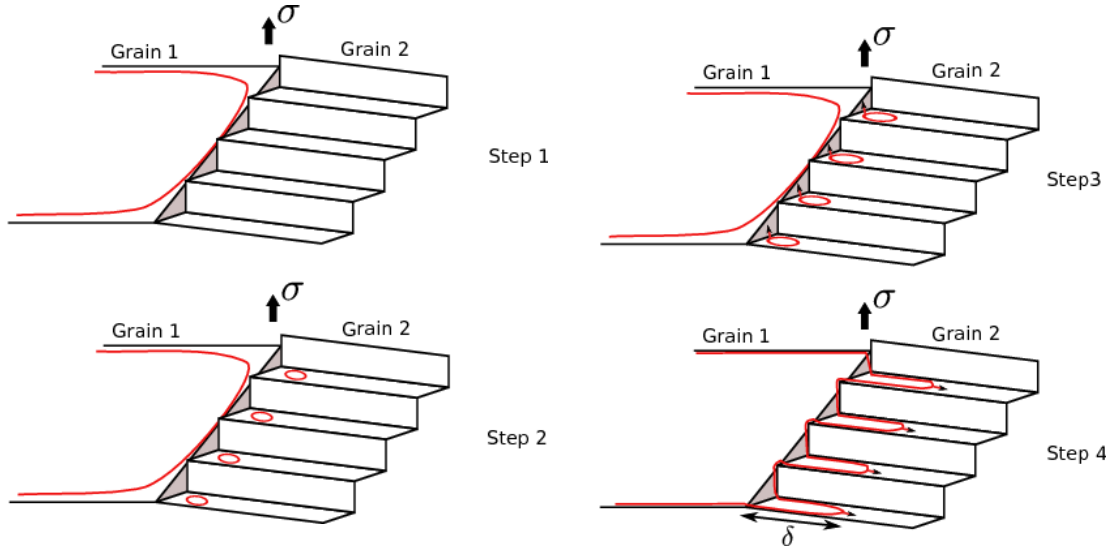


Figure 7. The four steps for a cleavage crack to cross a twisted grain boundary.

This model of grain boundary crossing has been used to identify the parameters introduced in the Beremin-type model for predicting the fracture toughness of inhomogeneous materials [2] in which two modes of failure (intergranular and cleavage) are competing. The results shown in Fig. 8 were obtained using  $V_o = (50 \text{ } \mu\text{m})^3$ ,  $m_B = m_{SZ} = 30$  (Weibull shape factors for base metal (B) and segregated zones (SZ)) in the as-received and aged conditions),  $f = 10 \%$  (volume fraction of segregated zones). The critical stresses were taken as:

$$\begin{aligned} \sigma_u^B &= 3300 \text{ MPa (as-received)}, \sigma_u^B = 3230 \text{ MPa (aged)}, \\ \sigma_u^{SZ} &= 3250 \text{ MPa (as-received)}, \sigma_u^{SZ} = 2750 \text{ MPa (aged)} \end{aligned}$$

It is thus observed that aging produces a small decrease of the cleavage stress (by about 2%), due to the mechanism for cleavage described in Figs. 6 & 7, and a larger decrease of the intergranular fracture stress in the segregated zones (by about 15%) due to phosphorus intergranular segregation after aging. This value is in good agreement with the measurements carried out on homogeneous material representing the composition of the segregated zones [18].

Fig. 8 shows that the bimodal model for fracture is able to reproduce the observed variations in fracture toughness with temperature in both conditions (as-received and aged). This model accounts also reasonably well for the shift in DBTT with aging ( $\sim 30^\circ\text{C}$  at  $K = 100 \text{ MPa}\sqrt{m}$  and  $P_r = 63 \%$ ). It accounts also for the increased scatter observed in test results on aged material. This model can also be used for predicting the variation of fracture toughness with longer aging times and lower

temperatures typical of those of in-service conditions.

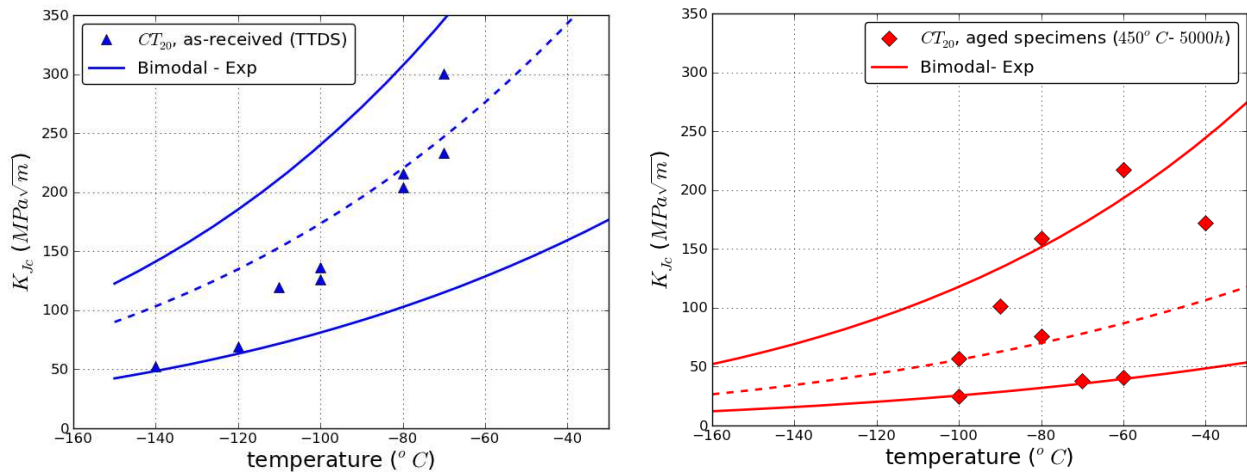


Figure 8. Variation of the fracture toughness with temperature. Experiments and predictions from Beremin-type bimodal model [2]. The calculated values corresponding to failure probabilities of 5%, 63% and 95% are shown.

## 6. Conclusions

1. Thermal aging of a 18MND5 plate (type A533B) at 450 $^{\circ}\text{C}$  for 5000 hours produces a shift of the ductile-to-brittle transition temperature (DBTT) of about 39 $^{\circ}\text{C}$ . This shift is not accompanied by a drastic change in fracture modes which remain partly intergranular in the segregated zones and transgranular cleavage in the matrix. The fracture toughness of aged material is much more scattered than that of the as-received material.
2. The slow cooling rate applied during cooling after the stress-relieving heat treatment ( $\sim 30^{\circ}\text{C}/\text{h}$ ) generates intergranular phosphorus segregation which is sufficient to provoke intergranular fracture in the segregated zones, even in the as-received conditions.
3. Auger spectrometry measurements showed that during aging at 450 $^{\circ}\text{C}$ , phosphorus continues to segregate along the grain boundaries, while carbon concentration at grain boundaries decreases. Both phenomena produce an embrittlement effect of the grain boundaries.
4. A model of intergranular segregation including the interaction between C and P atoms and non-isothermal conditions was identified. The results of this model were used as inputs for the prediction of bimodal fracture toughness of an inhomogeneous material representing the banded structure of the micro-segregated steel. The kinetics is represented using the McLean – Guttman – Militzer theories.
5. The variations in DBTT and in the scatter of fracture toughness test results induced by aging are correctly predicted using these models of segregation and of fracture toughness.

## Acknowledgments

This work has been made in the frame of the Areva - Ecole des Mines industrial professorship. Support from Areva is acknowledged. The authors would like to acknowledge also D. Loizon, S.

Cremel and O. Bouaziz from ArcelorMittal Research for Auger spectrometry measurements.

## References

- [1] C. Naudin, A. Pineau, J.- M. Frund, Numerical modeling of fracture toughness in RPV steel containing segregated zones in PVP 443-1, Fatigue, Fracture and Damage Analysis, ASME PVP 2002-1333, 2002, pp. 69-75.
- [2] A. Andrieu, A. Pineau, J. Besson, D. Ryckelynck, O. Bouaziz, Bimodal Beremin-type model for brittle fracture of inhomogeneous ferritic steels: Theory and applications, Eng. Fract. Mech. 95, 2002, pp. 84-101.
- [3] A. Pineau, Development of the local approach to fracture over the past 25 years: Theory and applications, Int. J. Fract. 138, 2006, pp. 139-166.
- [4] F. M. Beremin, A local criterion for cleavage fracture of a nuclear pressure vessel steel, Metall. Mater. Trans. A14, 1983, pp. 2277-2287.
- [5] A. Andrieu, A. Pineau, J. Besson, D. Ryckelynck, O. Bouaziz, Beremin model : Methodology and application to the prediction of the Euro toughness data set, Eng. Fract. Mech. 95, 2002, pp. 102-117.
- [6] D. McLean, Grain boundaries in metals, Oxford University Press, London, 1957.
- [7] M. Guttman, Ph. Dumoulin, M. Wayman, The thermodynamics of interactive cosegregation of phosphorus and alloying elements in iron and temper-brittle steels, Met. Trans. 13A, 1982, pp. 1693-1711.
- [8] K. Wallin, Fracture toughness of engineering materials, EMAS Publishing, Warrington, U.K., 2011.
- [9] ASTM standards E1921-97, Standard test method for determination of reference temperature,  $T_0$ , for ferritic steels in the transition range, 1997, pp. 1068-1084.
- [10] A. Andrieu, PhD thesis Ecole des Mines de Paris, 2013.
- [11] P. Lejcek, Grain boundary segregation in metals, Springer Heidelberg, Dordrecht, London, New York, 2010.
- [12] M. Militzer, J. Wieting, Theory of segregation kinetics in ternary systems, Acta Metall. 34, 1986, pp. 1229-1236.
- [13] S. G. Druce, G. Gage, G. Jordan, Effect of ageing on properties of pressure vessel steels, Acta Metall. 34, 1986, pp. 641-652.
- [14] C. A. Hippsley, S. G. Druce, The influence of phosphorus segregation to particle/matrix interfaces on ductile fracture in a high strength steel, Acta Metall. 31, 1983, pp. 1861-1872.
- [15] K.H.D.H. Badeshia, R.W.K. Honeycombe, Steels – Microstructure and properties, 3<sup>rd</sup> edition, Butterworth-Hennemann, Oxford, UK, 2006.
- [16] H. Erhart, H. J. Grabke, Equilibrium segregation of phosphorus at grain boundaries of Fe-P, Fe-C-P, Fe-Cr-P and Fe-Cr-C-P alloys, Metal Science 15, 1981, pp. 401-408.
- [17] J. R. Rice, J.- S. Wang, Embrittlement of interfaces by solute segregation, Mater. Sci. Engng A107, 1989, pp. 23-40.
- [18] C. Naudin, J.- M. Frund, A. Pineau, Intergranular fracture stress and phosphorous grain boundary segregation of a Mn-Ni-Mo steel, Scripta Mater. 40, 1999, pp. 1013-1019.
- [19] R. Ding, A. Islam, S. Wu, J. Knott, Effect of phosphorus segregation on fracture properties of two quenched and tempered structural steels, Mater. Sci. and Tech. 21, 2005, pp. 467-475.
- [20] Y. Qiao, A. S. Argon, Cleavage crack-growth resistance of grain boundaries in polycrystalline Fe-2% Si alloy: experiment and modeling, Mech. Materials 35, 2003, pp. 129-154.
- [21] W. Lu, J. Chen, X. Kong, S. S. Chakravarthula, Y. Qiao, Non uniform cleavage across persistent grain boundary, Mech. Materials 43, 2011, pp. 567-573.