

Sb or Nb doped tin dioxide aerogels based PEFC cathode

Guillaume Ozouf, Gwenn Cognard, Frédéric Maillard, Laure Guétaz, Marie Heitzmann, Christian Beauger

► **To cite this version:**

Guillaume Ozouf, Gwenn Cognard, Frédéric Maillard, Laure Guétaz, Marie Heitzmann, et al.. Sb or Nb doped tin dioxide aerogels based PEFC cathode. PRiME 2016 - 6th International ECS Electrochemical Energy Summit, The Electrochemical Society (ECS), The Electrochemical Society of Japan (ECSJ), and The Korean Electrochemical Society (KECS), Oct 2016, Honolulu, Hawaii, United States. hal-01426967

HAL Id: hal-01426967

<https://hal-mines-paristech.archives-ouvertes.fr/hal-01426967>

Submitted on 5 Jan 2017

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Sb or Nb doped tin dioxide aerogels based PEFC cathode

Guillaume Ozouf^a, Gwenn Cognard^{b,c}, Frédéric Maillard^{b,c}, Laure Guétaz^{d,e}, Marie Heitzmann^{d,e}, Christian Beauger^{a,*}

^a MINES ParisTech, PSL Research University PERSEE - Centre procédés, énergies renouvelables et systèmes énergétiques, CS 10207 rue Claude Daunesse 06904 Sophia Antipolis Cedex, France

^b Univ. Grenoble Alpes, LEPMI, F-38000 Grenoble, France

^c CNRS, LEPMI, F-38000 Grenoble, France

^d University Grenoble Alpes, Grenoble F-38000, France

^e CEA, LITEN, 17 rue des martyrs, F-38054 Grenoble, France

*corresponding author

Keywords: Fuel Cells, Catalysts support, Tin Dioxide, Aerogels, Catalytic Activity.

Catalyst supports for Polymer Electrolyte Fuel Cells (PEFC) are currently made up of carbon blacks. This material is however not thermodynamically stable in fuel cell operating conditions and loss of performance is observed with time, especially at the cathode side. To improve PEFC durability and make this technology a credible alternative to conventional power sources, carbon free cathodes were prepared. With a remarkable morphology, aerogels have already proven their ability to efficiently support catalysts for PEFC application [1, 2]. In this study doped tin dioxide aerogels are proposed as alternative support presumably stable in PEFC operating conditions.

Antimony and niobium doped tin dioxide aerogels were synthesized using sol-gel route in acidic media from alkoxide precursors. These materials have shown particularly adapted physico-chemical properties [3]. Platinum catalyst supported on doped SnO₂ aerogels was prepared by two methods. Method A was based on the impregnation of a platinum salt followed by a reduction under UV and a heat treatment in oxidative or reducing atmosphere. Method EG is a conventional polyol method using ethylene glycol. Electrocatalysts structures and morphologies were investigated by X-ray diffraction and transmission electron spectroscopy. Active Electrochemical Surface Areas (ECSA) and catalytic activities for oxygen reduction reaction (ORR) were measured on Rotating Disk Electrode (RDE). Method A leads to the formation of particularly well dispersed Pt nanoparticles on aerogel surface (Figure 1), whereas filament form was observed after the use of Method EG. Heat treatments have shown direct influence on Pt structure and crystallinity. Highest ECSA was recorded after method A (45 m². mg_{Pt}⁻¹) while highest ORR mass activity was measured after method EG (40 mA. mg_{Pt}⁻¹). This value is even higher than that of the chosen carbon based electrocatalyst reference, TEC10E40E, measured in the same conditions (23.4 mA. mg_{Pt}⁻¹). Half-cell and MEA singlecell test measurements will also be presented to complete the characterization panel.

The work presented here is funded by the European Union's Seventh Framework Program for the Fuel Cells and Hydrogen Joint Technology Initiative under grant agreement n325239 (FCH-JU project Nano-CAT) and the French National Research Agency PROGELEC programme, (ANR-12-PRGE-007 project SURICAT). It was supported by Capenergies and Tenerrdis.

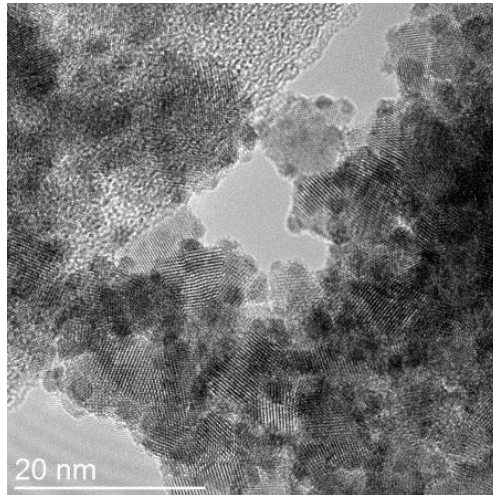


Figure 1. TEM image of a Pt/Sb doped (10 at%) SnO₂ aerogel from method A

REFERENCES

1. M. Ouattara-Brigaudet, S. Berthon-Fabry, C. Beauger, M. Chatenet, N. Job, M. Sennour, Influence of the carbon texture of platinum/carbon aerogel electrocatalysts on their behavior in a proton exchange membrane fuel cell cathode. *International Journal of Hydrogen Energy* 37, 9742-9757 (2012).
2. M. Ouattara-Brigaudet, C. Beauger, S. Berthon-Fabry, P. Achard, Carbon Aerogels as Catalyst Supports and First Insights on Their Durability in Proton Exchange Membrane Fuel Cells. *Fuel Cells* 11, 726-734 (2011).
3. G. Ozouf, C. beauger, Niobium- and antimony-doped tin dioxide aerogels as new catalyst supports for PEM fuel cells, *Journal of Materials Science* DOI 10.1007/s10853-016-9833-7 (2016)